

LIDT TEST RESULTS

LIDT VALUE

10^8 -on-1

$0.78^{+0.18}_{-0.17}$ J/cm²

CHARACTERISTIC DAMAGE CURVE

Table 1: Estimated LIDTs from fitting model for sample 930.

Test mode	Threshold (catastrophic)	Threshold (color change)
1-on-1	$1.700^{+0.063}_{-0.062}$ J/cm ²	-
10-on-1	$1.390^{+0.043}_{-0.042}$ J/cm ²	-
10 ² -on-1	$1.235^{+0.026}_{-0.025}$ J/cm ²	-
10 ³ -on-1	$1.230^{+0.025}_{-0.025}$ J/cm ²	-
10 ⁴ -on-1	$1.220^{+0.026}_{-0.025}$ J/cm ²	-
10 ⁵ -on-1	$1.211^{+0.034}_{-0.034}$ J/cm ²	$1.15^{+0.05}_{-0.05}$ J/cm ²
10 ⁶ -on-1	$1.211^{+0.034}_{-0.034}$ J/cm ²	$1.01^{+0.04}_{-0.04}$ J/cm ²
10 ⁷ -on-1	$1.129^{+0.037}_{-0.037}$ J/cm ²	$0.92^{+0.04}_{-0.04}$ J/cm ²
10 ⁸ -on-1	$1.119^{+0.047}_{-0.046}$ J/cm ²	$0.78^{+0.18}_{-0.17}$ J/cm ²

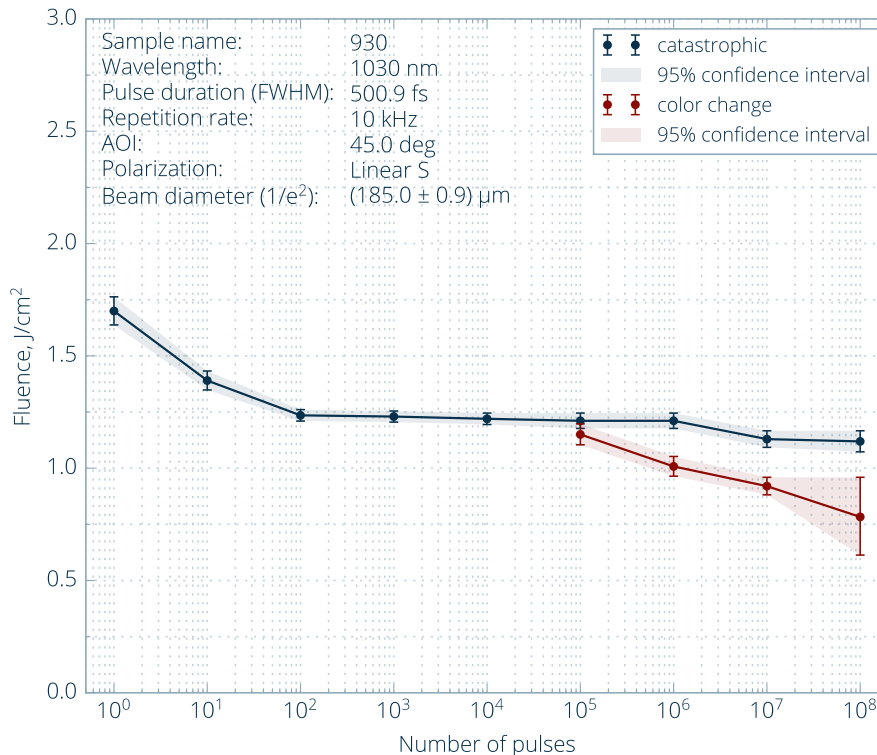


Figure 2. Characteristic damage curve.