

# LIDT TEST RESULTS

## LIDT VALUE

$10^6$ -on-1

$0.306^{+0.037}_{-0.037}$  J/cm<sup>2</sup>

## CHARACTERISTIC DAMAGE CURVE

Table 1: Estimated LIDTs from fitting model for sample HL\_F5\_S1.

Test mode	Threshold (Catastrophic)	Threshold (Color mode)
1-on-1	$>0.476^{+0.051}_{-0.051}$ J/cm <sup>2</sup>	-
10-on-1	$>0.476^{+0.051}_{-0.051}$ J/cm <sup>2</sup>	-
$10^2$ -on-1	$0.380^{+0.042}_{-0.042}$ J/cm <sup>2</sup>	-
$10^3$ -on-1	$0.380^{+0.042}_{-0.042}$ J/cm <sup>2</sup>	-
$10^4$ -on-1	$0.339^{+0.037}_{-0.037}$ J/cm <sup>2</sup>	-
$10^5$ -on-1	$0.339^{+0.037}_{-0.037}$ J/cm <sup>2</sup>	$0.391^{+0.055}_{-0.053}$ J/cm <sup>2</sup>
$10^6$ -on-1	$0.339^{+0.037}_{-0.037}$ J/cm <sup>2</sup>	$0.306^{+0.037}_{-0.037}$ J/cm <sup>2</sup>

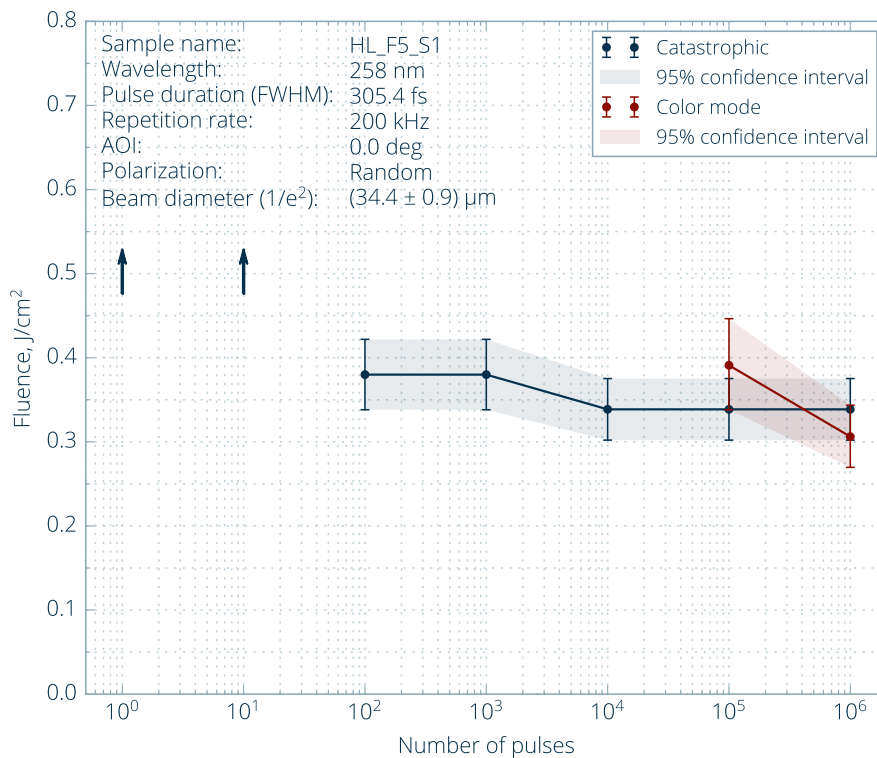


Figure 2. Characteristic damage curve.