

# LIDT TEST RESULTS

## LIDT VALUE

$10^6$ -on-1	$1.084^{+0.037}_{-0.037} \text{ J/cm}^2$
--------------	--

## CHARACTERISTIC DAMAGE CURVE

Table 1: Estimated LIDTs from fitting model for sample CAM71-opt.

Test mode	Threshold (Catastrophic)	Threshold (Color mode)
1-on-1	$1.612^{+0.056}_{-0.055} \text{ J/cm}^2$	-
10-on-1	$1.332^{+0.068}_{-0.067} \text{ J/cm}^2$	-
$10^2$ -on-1	$1.241^{+0.056}_{-0.055} \text{ J/cm}^2$	-
$10^3$ -on-1	$1.193^{+0.025}_{-0.025} \text{ J/cm}^2$	-
$10^4$ -on-1	$1.183^{+0.032}_{-0.032} \text{ J/cm}^2$	-
$10^5$ -on-1	$1.181^{+0.030}_{-0.030} \text{ J/cm}^2$	-
$10^6$ -on-1	$1.181^{+0.030}_{-0.030} \text{ J/cm}^2$	$1.084^{+0.037}_{-0.037} \text{ J/cm}^2$

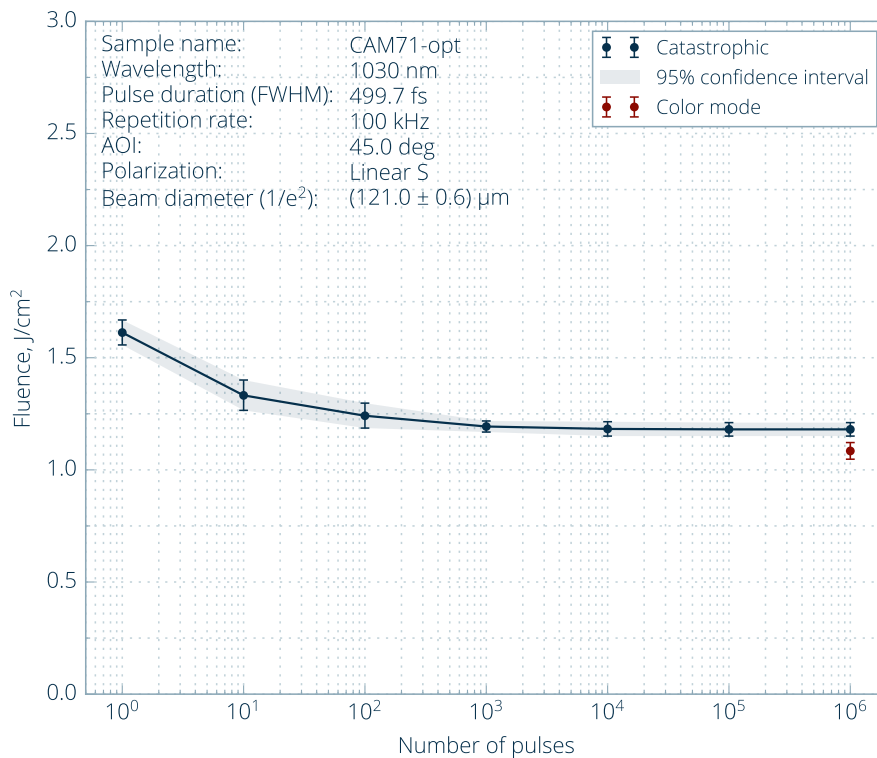


Figure 2. Characteristic damage curve.